


Analysis of Volatile Substances in Accordance with Testing of Polystyrene Materials - Using InertCap WAX

As a material test for synthetic resins that contain polystyrene as the main component, the total of volatile substances has been stipulated in the required specifications. This application note presents an example of the measurement of volatile substances in instant food containers using a GC/FID method with a capillary column in accordance with the test method defined in the Standards for Instruments and Containers and Packaging and the test method.

Example: Measurement of standard

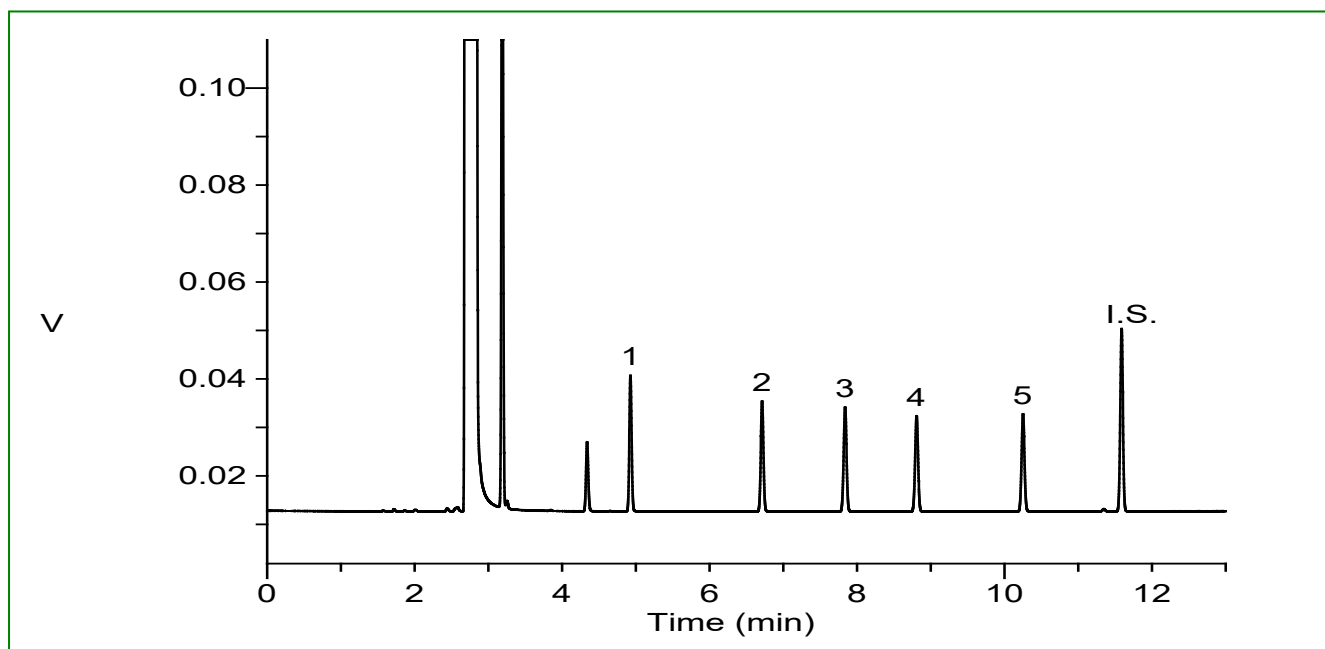


Conditions


System	: GC - FID
Column	: InertCap WAX 0.25 mm I.D. x 30 m df = 0.50 μ m
Col.Temp.	: 60 °C - 4 °C/min - 100 °C - 10 °C/min - 200 °C
Carrier Gas	: He 120 kPa
Injection	: Split 1:20 220 °C
Detection	: FID Range 10 ¹⁰ 220 °C
Sample Size	: 25 μ g/mL in THF 1.0 μ L

Analyte:


1. Toluene
 2. Ethylbenzene
 3. Cumene
 4. N-Propylbenzene
 5. Styrene
- I.S. Diethylbenzene




1. Toluene




2. Ethylbenzene



3. Cumene





4. N-Propylbenzene



5. Styrene


Calibration curve

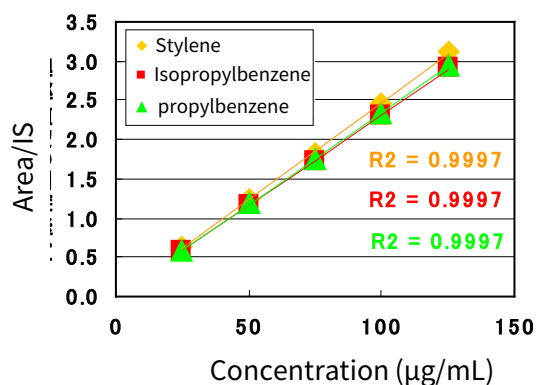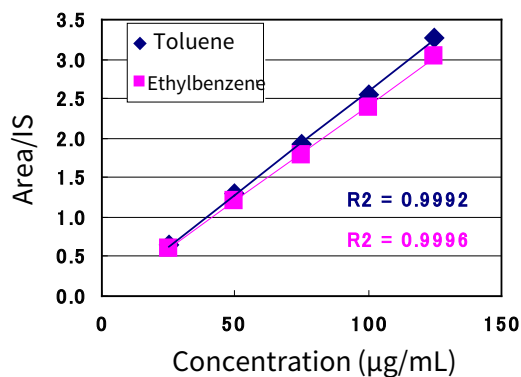

Example: Measurement of instant noodle container

For measurement, 0.5 g of an instant noodle container was weighed and dissolved in 20 mL of THF.

Ethylbenzene and styrene were detected in the containers, but the value was found to be 1.0 mg/g or less, which is the accepted standard for expanded polystyrene using hot water.

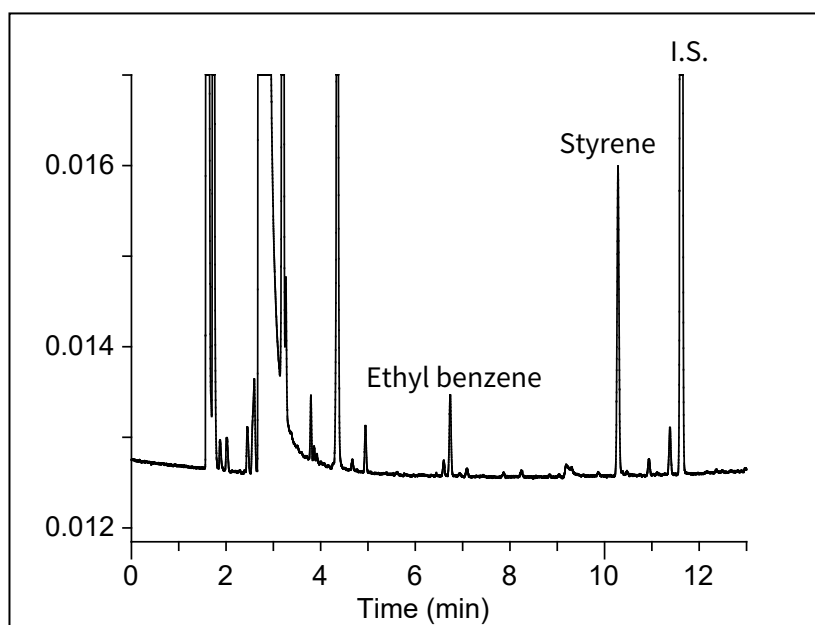

GL Sciences disclaims any and all responsibility for any injury or damage which may be caused by this data directly or indirectly. We reserve the right to amend this information or data at any time and without any prior announcement.

GL Sciences Inc. Japan

22-1 Nishishinjuku 6-chome
Shinjuku-ku, Tokyo
163-1130, Japan

Phone: +81-3-5323-6620
Fax: +81-3-5323-6621
Email: world@glsc.co.jp
Web: www.glsciences.com

GL Sciences Inc. USA

4733 Torrance Blvd. Suite 255
Torrance, CA 90503
USA

Phone: +1-310-265-4424
Fax: +1-310-265-4425
Email: info@glsciencesinc.com
Web: www.glsciencesinc.com

GL Sciences B.V.

Dillenburgstraat 7C
5652AM, Eindhoven
The Netherlands

Phone: +31-40-254-9531
Email: info@glsciences.eu
Web: www.glsciences.eu

GL Sciences (Shanghai) Limited

Tower B, Room 2003
Far East International Plaza
No.317 Xianxia Road, Changning District
Shanghai, China 200051

Phone: +86-21-62782272
Email: contact@glsciences.com.cn
Web: www.glsciences.com.cn



International Distributors

Visit our Website at www.glsciences.com/distributors